



This article appeared in a journal published by Elsevier. The attached copy is furnished to the author for internal non-commercial research and education use, including for instruction at the authors institution and sharing with colleagues.

Other uses, including reproduction and distribution, or selling or licensing copies, or posting to personal, institutional or third party websites are prohibited.

In most cases authors are permitted to post their version of the article (e.g. in Word or Tex form) to their personal website or institutional repository. Authors requiring further information regarding Elsevier's archiving and manuscript policies are encouraged to visit:

<http://www.elsevier.com/copyright>



Contents lists available at SciVerse ScienceDirect

## Journal of Non-Crystalline Solids

journal homepage: [www.elsevier.com/locate/jnoncrysol](http://www.elsevier.com/locate/jnoncrysol)

## Study on the effectiveness of thermally treated rice husks for petroleum adsorption

Kudaybergenov Kenes<sup>\*</sup>, Ongarbayev Yerdos, Mansurov Zulkhair, Doszhanov Yerlan*al-Farabi Kazakh National University, Institute of Combustion Problems, 050012, Almaty, Republic of Kazakhstan*

## ARTICLE INFO

## Article history:

Received 3 May 2012

Received in revised form 3 July 2012

Available online 12 August 2012

## Keywords:

Thermally treated rice husk;

Petroleum spills;

Water pollution;

Adsorbent;

Clean-up

## ABSTRACT

Rice husks, an agricultural waste, were thermally treated and evaluated as an adsorbent for petroleum with the aim of being used as a remediation strategy for petroleum spills. The petroleum sorption capacity was examined for thermally treated rice husks, which mainly composed of amorphous SiO<sub>2</sub>. Results showed that the petroleum sorption capacity of this material prepared at 700 °C was 15 g/g for heavy crude petroleum. The effects of heating temperature, contact time and petroleum density on the petroleum sorption capacity of thermally treated rice husks were further studied on the basis of phase composition, microstructure and morphology using X-ray diffraction analysis, FTIR spectrometry and scanning electron microscopy (SEM).

© 2012 Elsevier B.V. All rights reserved.

## 1. Introduction

Large-scale petroleum spills in aquatic environments commonly occur during the production, transportation, refining and storage of crude oil. This can cause major environmental problems due to the toxicity of many compounds in petroleum to aquatic organisms, birds and humans [1–3]. It has been estimated that petroleum is annually spilled on the surface of the ocean in amounts between 10,000,000 and 20,000,000 tons, whereby a ton of it may cover about 12 km<sup>2</sup> of the ocean's surface [4]. Moreover, the toxic volatile constituents of petroleum spills can evaporate and as a consequence, cause atmospheric pollution. Thus, clean-up of petroleum spills from the water surface is an important task.

Different methods can be used for the removal of petroleum from the water surface, for example, thermal, biological, mechanical and physico-chemical (using coagulants and adsorbent materials) techniques. So far, removing of petroleum spills by adsorbent materials is the most safety and effective processes. Different types of adsorbents including chrome shavings [2], raw cotton and sand [5], feathers [6], wool and sepiolite [7], peat [8], exfoliated graphite [9], vermiculite [10], silica aerogels, zeolites, organoclays [11] and nonwoven polypropylene [12] have been investigated in this context. Among various reports, most of these petroleum adsorbents were found to have high costs or poor buoyancy after petroleum sorption compared to agricultural waste materials.

In recent years, there has been a growing interest in the production of adsorbents from agricultural wastes for petroleum spills clean-up such as garlic and onion peel [1], barley straw [3], banana trunk fibers [13], kapok [14], walnut shell [15], pith bagasse [16] rice straw [17] and rice husk [4,18]. The adsorbents on the base of rice husk are widely

used in various processes including the purification and recovery of valuable substances from liquid and gaseous media. For example, treated and untreated rice husks were studied as adsorbent materials for the removal of 2,4-dichlorophenol [19], formaldehyde and acetaldehyde [20], free fatty acids [21,22], phenol [23], pyridine [24], metal ions [25], ammonium ions [26], methylene blue [27] and humic acids [28] in aqueous systems. Thus, rice husks may be also a suitable source for obtaining valuable adsorbent materials with high specific surface area and large pore volume by thermal treatment.

Rice husks are an agricultural waste that incurs annually at 545 million tons [29]. Typically, rice husks consist of about 75% organic substances (cellulose, lignin, hemicelluloses), 15% amorphous SiO<sub>2</sub>, 10% water and microelements [30]. Thus, converting rice husks into petroleum adsorbents can solve two environmental problems: utilization of an agricultural waste and remediation of contaminated aquatic environments. The advantages of petroleum adsorbents obtained from rice husks are their ecological safeness, origin from a broad source of raw materials, floatability after petroleum sorption, high hydrophobicity, low costs and porous structure after thermal treatment that provides a high sorption capacity.

Thermally untreated rice husks have been investigated in several studies [4,18] for petroleum removal. However, its sorption capacity was relatively low because untreated rice husks are nonporous. On the other hand, the petroleum sorption capacity of rice husks can be increased after thermal treatment due to the enhancement of its surface area and pore volume [31].

The aim of the present study was to investigate the petroleum sorbent efficiency of thermally treated rice husks for the removal of heavy crude petroleum and petroleum products from the water surface and the physicochemical characteristics of the obtained adsorbents. For this, the petroleum adsorbent was prepared by thermal treatment under a CO<sub>2</sub> atmosphere.

<sup>\*</sup> Corresponding author. Tel.: +7 775 993 09 93; fax: +7 727 292 58 11.  
E-mail address: [kenes\\_85\\_85@mail.ru](mailto:kenes_85_85@mail.ru) (K. Kenes).

## 2. Materials and methods

### 2.1. Sample preparation

The samples were thermally treated according to the procedure developed at R.M. Mansurova Laboratory of Carbon Nanomaterials at the Institute of Combustion Problems [31]. Rice husks were washed with water to remove dirt, then oven-dried at about 110 °C for 24 h. The dried rice husks were placed in a steel reactor and heated in a muffle furnace under CO<sub>2</sub> flow (200 ml/min) at 300–800 °C for 1 h and the resulting thermally treated rice husks (TRH) were designated as TRH<sub>300</sub>, TRH<sub>400</sub>, TRH<sub>500</sub>, TRH<sub>600</sub>, TRH<sub>700</sub> and TRH<sub>800</sub>, respectively.

### 2.2. Methods

X-ray phase analysis (XPA) of thermally treated samples was performed with DRON-3M diffractometer at an accelerating voltage of 30 kV using tubes with a copper cathode. Recording was performed at a rate of 2 deg/min with an angle range of 5 to 50°. The samples were crushed into powder and placed on glass cuvettes greased with Vaseline.

IR spectra of the samples (tablets pressed with KBr) were recorded with an IR spectrometer (Nicolet-5700) in the wave number range from 4000 to 400 cm<sup>-1</sup> with Fourier transformation.

The specific surface of the samples was determined by the BET method using a SORBTOMETR-M apparatus.

The microstructures and microanalysis of adsorbents were investigated with an SEM (Quanta 3D 200i, USA) at an accelerated voltage of 20 kV and a pressure of 0.003 Pa (performed by National Nanotechnology Laboratory of Open Type of Kazakh National University).

The sorption capacities of the samples were evaluated with petroleum products of different density: gasoline AI-80 ( $\rho = 0.734$  g/cm<sup>3</sup>); diesel fuel ( $\rho = 0.818$  g/cm<sup>3</sup>); industrial petroleum ( $\rho = 0.886$  g/cm<sup>3</sup>); heavy crude petroleum ( $\rho = 0.937$  g/cm<sup>3</sup>) and light crude petroleum ( $\rho = 0.792$  g/cm<sup>3</sup>). The petroleum sorption properties of the samples were determined using the procedure described in [32]. For that purpose 1 g adsorbent material was placed in an unwoven fabric pack then immersed into the petroleum (200 ml) or petroleum products. The sample was left in the petroleum for 30 min without any agitation. The unwoven fabric pack with adsorbent material was taken out of petroleum and drained of excess oil for 10 min then weighed. The experiment is conducted at room temperature.

The petroleum sorption capacity (PSC) of the sample was calculated according to the equation:

$$\text{PSC} = (M_1 - M_2) - 1;$$

where  $M_1$  is the mass of the petroleum adsorbed by the unwoven fabric pack with adsorbent material and  $M_2$  is the mass of the petroleum adsorbed by the unwoven fabric pack without adsorbent material.

The sorption procedure was carried out at different time intervals up to the equilibrium time.

## 3. Results and discussion

### 3.1. Petroleum sorption of rice husks thermally treated at different temperatures

The effects of heating temperature on the petroleum sorption capacity of the adsorbent materials were studied. Fig. 1 shows the relationship between heating temperature and the amount of heavy crude petroleum absorbed by thermally treated rice husk (TRH). One can see in Fig. 1 that the sorption capacity of TRH increased with increasing heating temperature from 300 to 700 °C and absorbed approximately 15 g/g of petroleum, then at higher temperature, the sorption capacity decreased. This can be explained by the fact that at higher temperature

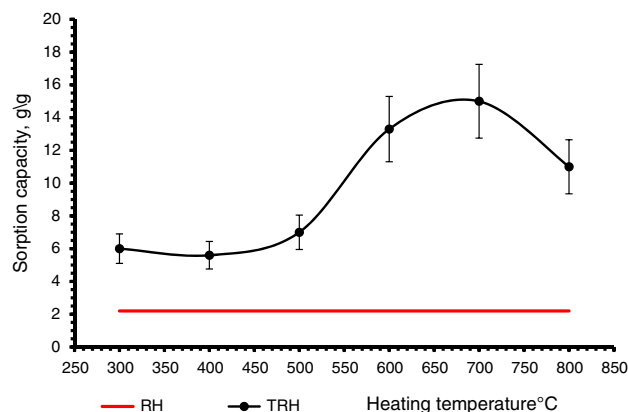


Fig. 1. Effect of heating temperature on heavy crude petroleum sorption properties of TRH<sub>700</sub> and RH.

caused a phase transformation of silica from amorphous to crystalline form and hence decreasing the sorption capacity of TRH [27]. Comparing the experimental data shows that TRH had the highest sorption ability, while virgin rice husk (RH) had the lowest one; this is likely to be connected with the high density of thermally untreated rice husk. For further studies, thermally treated rice husk (TRH<sub>700</sub>) was selected as petroleum adsorbent. The experimental observations show that TRH float on the surface water after petroleum sorption because the TRH has a lower density than virgin rice husk [32].

The effect of contact time on the sorption capacity of TRH<sub>700</sub> was studied. Fig. 2 shows that the sorption capacity of TRH<sub>700</sub> increased with the contact time from the first 5 min on, then it reached equilibrium. Also, this curve consists of two phases (rapid phase and slow phase). This effect can be explained as follows: the thermally treated rice husk first absorbed petroleum by macropores and afterwards it penetrated into the micropores until reaching equilibrium time. The equilibrium times for heavy crude petroleum on TRH<sub>700</sub> and RH were 25 and 10 min, respectively. Summarizing the results, following optimum conditions can be inferred for heavy crude petroleum sorption by TRH<sub>700</sub>: heating temperature 700 °C and sorption time 25 min (Figs. 1 and 2).

### 3.2. The influence of petroleum products density on the sorption capacity of TRH<sub>700</sub> and RH

The influence of petroleum products density on the sorption capacity of thermally treated rice husks and virgin rice husks are shown in Fig. 3. The sorption capacity of samples increased with the increase of petroleum products' density. Thus the sorption capacity increased three times for TRH<sub>700</sub> and four times for the RH, whereby the absolute sorption of TRH<sub>700</sub> was much higher than that of RH. This effect may be due to less

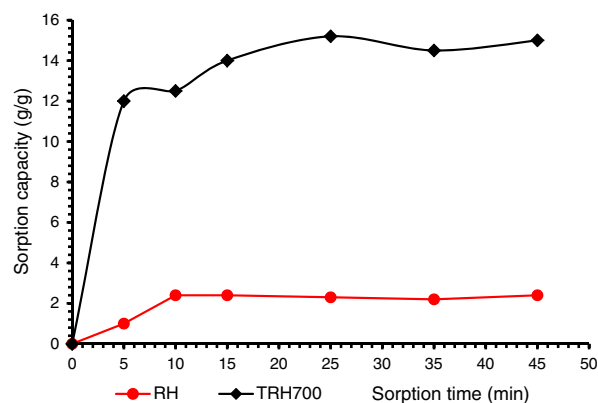


Fig. 2. Effect of contact time on sorption of heavy crude petroleum on TRH<sub>700</sub> and RH.

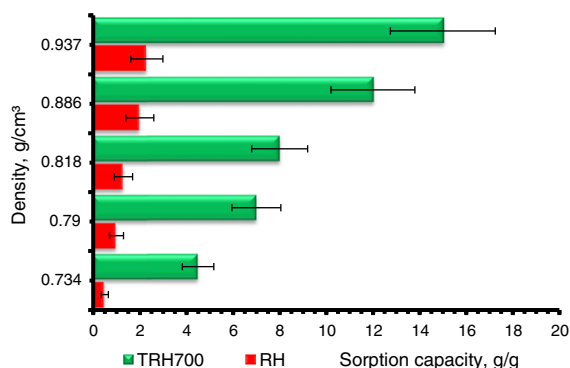


Fig. 3. Influence of adsorbate density on the sorption capacity for TRH<sub>700</sub> and RH.

retention of petroleum products into the pores of RH. As a result, gasoline (AI-80) with the lowest density ( $\rho = 0.734 \text{ g/cm}^3$ ) showed low sorption for the sorbent materials, while the heavy crude petroleum ( $\rho = 0.937 \text{ g/cm}^3$ ) indicated a high sorption. The influence of the density of petroleum products on the sorption capacity of the adsorbent materials was also investigated with similar result in earlier study [3]. Our results confirm that petroleum sorption depends both on the adsorbent material and the adsorbate type.

### 3.3. The influence of heating temperature on the specific surface area of TRH

The petroleum sorption by adsorbent materials is dependent on the specific surface area of the latter and hence on the adsorbent preparation process. The effect of the heating temperature on the surface area of rice husks is shown in Fig. 4. The specific surface area increased with increasing heating temperature up to 700 °C, however, the further increase of temperature caused a decrease of the specific surface area. The increasing of the specific surface area can be explained by formation of new micro- and mesopores during the thermal treatment [33]. The decrease of specific surface area after stronger heating of rice husks may be connected with the increase of density due to phase transformation of amorphous  $\text{SiO}_2$  into its cristobalite form. A similar result was reported by Chandrasekhar et al. [34]. The largest surface area of TRH was obtained at 700 °C and hence the adsorbent obtained that way had the highest sorption capacity for petroleum products.

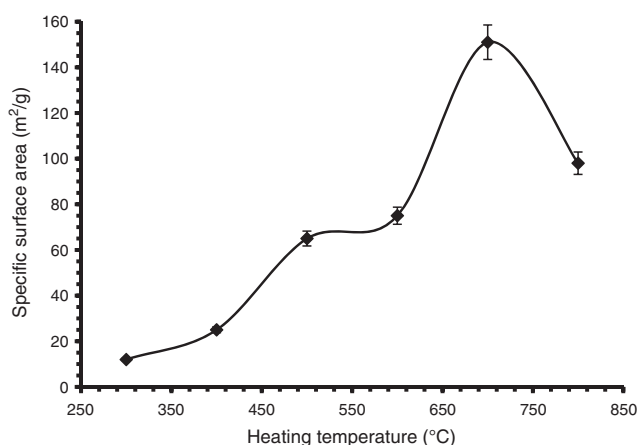


Fig. 4. Effect of heating temperature on the surface area of TRH.

### 3.4. Element analysis of rice husk samples thermally treated at different temperatures

Petroleum adsorption by thermally treated rice husks is seemingly dependent on their chemical composition. Figs. 5 and 6 summarize the results of microanalyses of TRH<sub>700</sub> using SEM/EDAX. In Fig. 5 (a) and (b), the variation of weight percent of four elements (Si, C, Al, K) in the heated rice husks is given for different temperatures. While the weight percentage of silicon and potassium increased with increasing heating temperature, the amount of aluminum and carbon decreased. The results of XRD analyses show that thermally treated rice husk consist mainly of amorphous silica (Fig. 7). Thereby, the element silicon in the thermally treated rice husk most probably existing as silica. In detail, the weight percentage of silicon in rice husk increased from 19.4% at 300 °C to 40.1% at 700 °C, and the carbon content decreased from 32.6% at 300 °C to 9.0% at 600 °C but increased again to 12.3% at 800 °C. This can be explained by the fact that higher temperatures cause the thermal decomposition of organic substances in the rice husks and hence the relative silica content increases [35]. Increasing weight percent of silica positively influences the petroleum sorption capacity of rice husk due to the good adsorbent properties of silica ( $\text{SiO}_2$ ). Fig. 6 shows that the principal element in TRH<sub>700</sub> is silica.

### 3.5. X-ray phase analysis of rice husks thermally treated at 400 °C and 700 °C

The rice husks thermally treated at 400 °C and 700 °C were investigated by X-ray diffraction. No difference was observed between XRD patterns of TRH<sub>700</sub> and TRH<sub>400</sub> (Fig. 7). The XRD pattern features two diffused peaks at  $2\theta = 22^\circ$  and at  $2\theta = 44^\circ$ , which corresponds to the presence of amorphous silica and graphite structures, respectively [35]. As seen

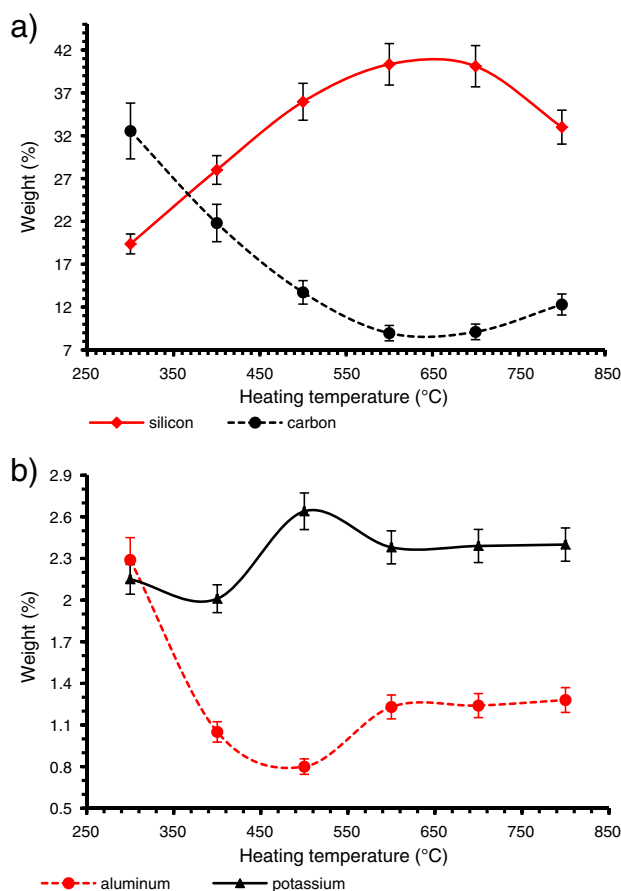


Fig. 5. Variation of weight percentage of silicon, carbon (a) and potassium, aluminum (b) in TRH produced at different temperatures.

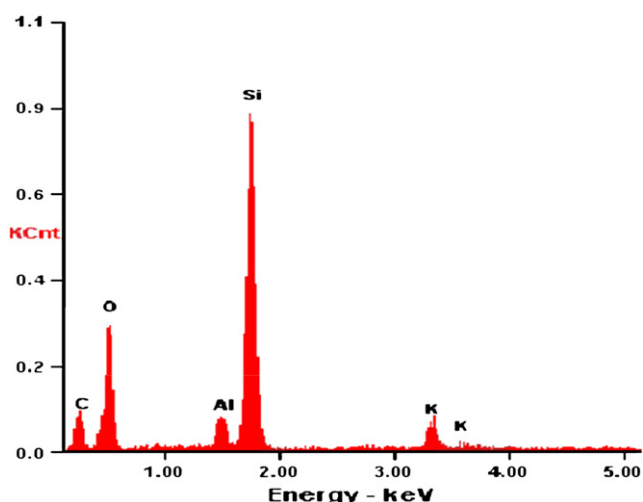


Fig. 6. Microanalysis of TRH<sub>700</sub> using SEM/EDAX.

from Table 1, the full width at half maximum (FWHM 2-Theta) is higher in case of the 400 °C sample, which indicates a smaller size of crystalline carbon. At higher temperatures, the FWHM 2-Theta may decrease due to the destruction of cellulose structures in rice husk. In this sample, probably calcite (CaCO<sub>3</sub>) was present in small amounts (less than 1.0 %). The integral intensity of the amorphous phase (net Area—cps×2-Theta) was highest in the 700 °C sample. In summary, it can be concluded from the XRD patterns that thermally treated rice husk mainly consist of amorphous silica.

### 3.6. IR-analysis of rice husks thermally treated at 400 °C and 700 °C

Thermally treated rice husks were also investigated by IR spectroscopy to determine functional groups on the surface of the samples. Fig. 8 (a), (b) and (c) show respective IR spectra of rice husks thermally treated at 400 °C and 700 °C and after petroleum sorption, respectively. The IR spectrum of TRH<sub>400</sub> contained intensive absorption bands at 3384, 2922, 2852, 1599, 1453, 1383 and 1089 cm<sup>-1</sup>. The broad peak at about 3384 cm<sup>-1</sup> may correspond to the —O—H-stretching vibrations of water molecules. The characteristic absorption bands at 2852 cm<sup>-1</sup> and 2922 cm<sup>-1</sup> are related to the —C—H stretching vibrations of methylene groups [36]. The peak at 1599 cm<sup>-1</sup> can be attributed to the —CO stretching vibrations of carbonyl groups in aldehydes and ketones. The double peak at 1453 and 1383 cm<sup>-1</sup> corresponds to the —C—O groups stretching of carboxylates. The pronounced peak at 1089 cm<sup>-1</sup> with high intensity is attributed to the stretching vibrations of siloxane groups [35]. Fig. 8 (b) shows the modified IR spectrum of

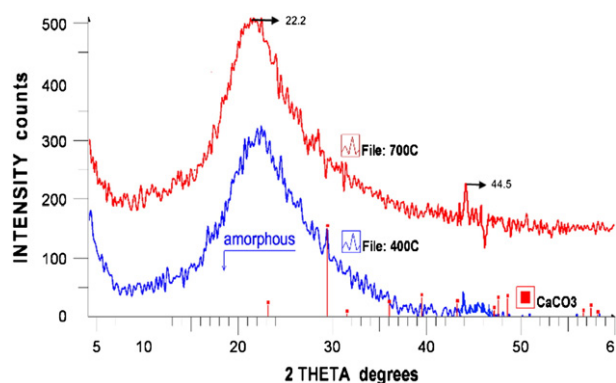


Fig. 7. XRD of the rice husk thermally treated at 400 °C and 700 °C.

Table 1  
XRD analysis of thermally treated rice husks.

Sample TRH	Obs. Max 2-Theta °	d (Obs. Max) Angstrom	FWHM 2-Theta °	Net Area Cps×2-Theta °
400°C	22.2	3.9658	8.999	2856.9
700°C	22.2	3.9571	8.161	3195.6
	44.5			

TRH<sub>700</sub>. The peaks at 2922 and 2852 cm<sup>-1</sup> disappeared when the heating temperature was increased from 400 to 700 °C. This indicates the evolution of CO<sub>2</sub> at higher temperature; i. e. residual methylene group may decompose. Fig. 8 (c) shows an IR spectrum of TRH<sub>700</sub> after petroleum sorption. One can see the emerging of sharp peaks at 2923 and 2853 cm<sup>-1</sup> indicating that petroleum components were bound to the hydrophobic groups of TRH<sub>700</sub>.

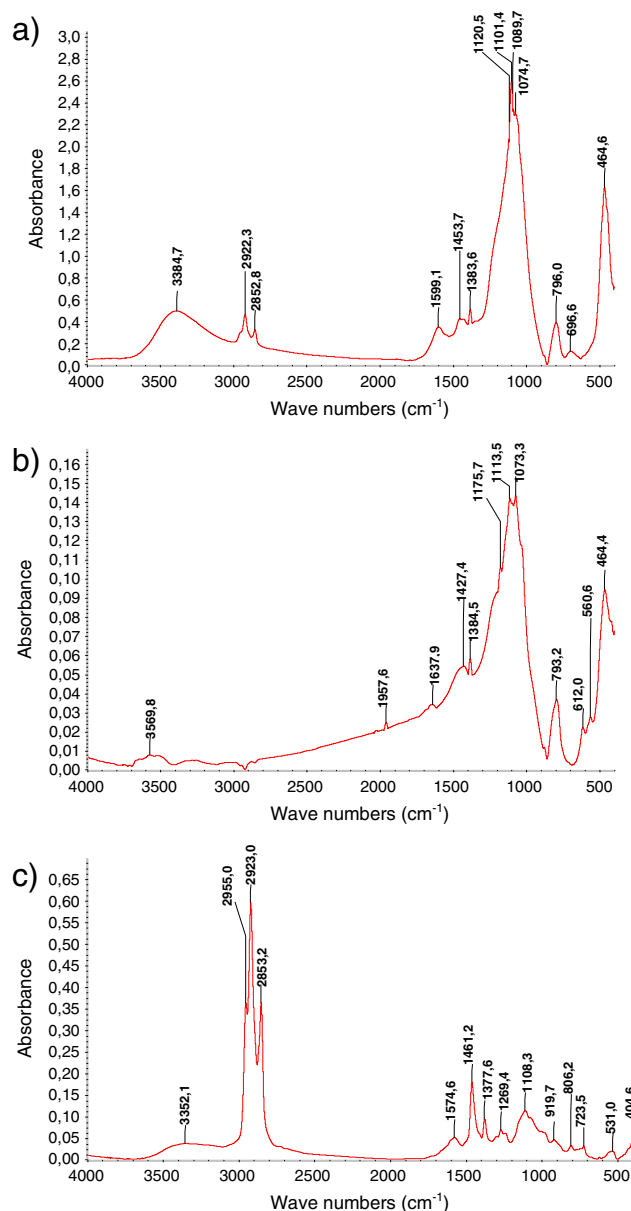


Fig. 8. FTIR spectra of TRH: (a) TRH<sub>400</sub>; (b) TRH<sub>700</sub> and (c) TRH<sub>700</sub> after petroleum sorption.



### 3.7. SEM study of virgin and thermally treated samples

The photographs in Fig. 9 depict the microstructure of virgin and thermally treated husk materials. The SEM image of virgin rice husks (Fig. 9 a) shows spherical silica particles of varying form on the organic matrix that consists of cellulose, hemicelluloses and lignin. Furthermore, it is visible that virgin rice husks are compact and do not contain any pore.

The external wall of TRH<sub>400</sub> shows the occurrence of a large number of button-like structures with small pores, which were not found in the virgin rice husk particles (Fig. 9 b). The emerging of pores and button-like structures may be caused by the fast removal of volatile organic

components from the particle [37]. A cross-section of TRH<sub>400</sub> is shown in Fig. 9 (c) and illustrates the presence of pores and channels in the particles with the diameters of about 5–10  $\mu\text{m}$ . The emerging of channels during combustion of rice husk has been discussed earlier in ref. [29]. The interior structure of TRH<sub>400</sub> (Fig. 9 d) furthermore indicates the formation of backbone-like structures during combustion [22]. Fig. 9 (e) shows again a cross-section (TRH<sub>700</sub>) that illustrates the distribution of mesopores and macropores in the rice husk particles emerged after treatment at 700 °C. The particles underwent drastic changes in this process of high-temperature treatment. Pores increased both in number and size, new types appeared, two or more smaller pores merged into bigger ones, and the surface and volume of pores changed.

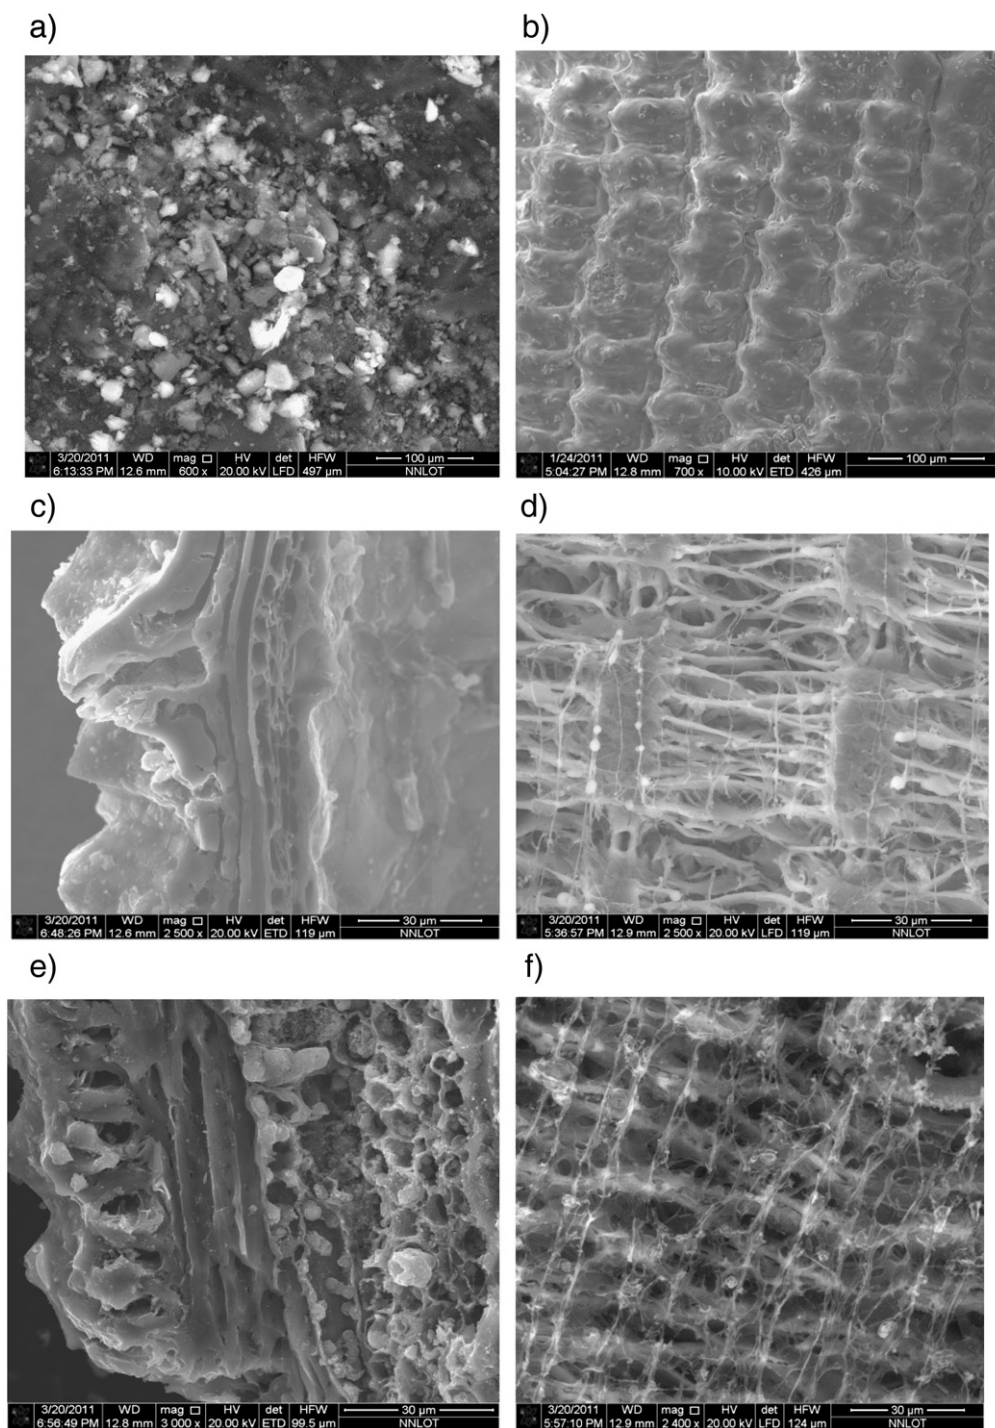


Fig. 9. SEM images of RH and TRH; (a) RH, (b, c, d) TRH<sub>400</sub> and (e, f) TRH<sub>700</sub>.

Fig. 9 (e) is similar to Fig. 9 (c), but the number of pores in TRH<sub>700</sub> is higher than in TRH<sub>400</sub> as well as their size are larger. Eventually, the interior structure of TRH<sub>700</sub> (Fig. 9 f) shows the converting of backbone-like structures into reticulated structures.

High petroleum sorption ability is determined by the porous structure of adsorbents, as well as by the physical and chemical interactions of their functional groups with the crude oil components. One can see in SEM images that thermal treatment allows to obtain a drastically modified structure with higher porosity compared to the virgin husk samples.

#### 4. Conclusions

Thermally treated adsorbents based on rice husks are an efficient absorber for heavy crude petroleum and petroleum products, since they possess high porosity and reactive surface functionalities including carboxyl, carbonyl and methylene groups. The results of the SEM studies strongly indicate that thermal treatment is a suitable method to improve structure of husk particles regarding porosity compared to virgin samples. The results of XRD and SEM/EDAX microanalyses show that thermally treated rice husk consist mainly of amorphous silica (SiO<sub>2</sub>). The optimal conditions for the treatment are as follows: heating temperature 700 °C and sorption time 25 min in case of heavy crude petroleum; under these conditions, the maximum sorption capacity of TRH<sub>700</sub> reached about 15 g petroleum per gram of husks. In conclusion, this study demonstrates the possibility to obtain effective petroleum adsorbents from rice husks, which are currently considered to be an agricultural waste.

#### References

- [1] S.A. Sayed, A.M. Zayed, Investigation of the effectiveness of some adsorbent materials in oil spill clean-ups, *Desalination* 194 (2006) 90–100.
- [2] A. Gammoun, S. Tahiri, A. Albizane, M. Azzi, J. Moros, S. Garrigues, M. de la Guardia, Separation of motor oils, oily wastes and hydrocarbons from contaminated water by sorption on chrome shavings, *J. Hazard. Mater.* 145 (2007) 148–153.
- [3] M. Hussein, A.A. Amer, A. El-Maghraby, N.A. Taha, Availability of barley straw application on oil spill cleanup, *Int. J. Environ. Sci. Tech.* 6 (1) (2009) 123–130.
- [4] J. Mortensen, Y. Huang, D. Viola, J. Belinda, X. Rmbo, S. Tony, Rice husks and oil pollution, Basic Studies in the Natural Sciences, RUC, Roskilde University, 2005. <http://rudar.ruc.dk/bitstream/1800/2281/1/Rice%20husks%20and%20oil%20pollution.pdf>.
- [5] F. Ray, C. Onuma, K. Serge, Xi Yunfei, Selected adsorbent materials for oil spill cleanup – a thermoanalytical study, *J. Therm. Anal. Calorim.* 91 (3) (2008) 809–816.
- [6] E. Cervantes-González, L.I. Rojas-Avelizapa, R. Cruz-Camarillo, Feather Waste as Petroleum Sorbent: A Study of its Structural Biodegradation, In: Proceedings of the Annual International Conference on Soils, Sediments, Water and Energy, vol. 13, Art 7, 2008, pp. 50–58, <http://scholarworks.umass.edu/soilsproceedings/vol13/iss1/7>.
- [7] V. Rajaković-Ognjanović, G. Aleksić, Lj. Rajaković, Governing factors for motor oil removal from water with different sorption materials, *J. Hazard. Mater.* 154 (2008) 558–563.
- [8] S. Suni, A.L. Kosunen, M. Hautala, A. Pasila, M. Romantschuk, Use of a by-product of peat excavation, cotton grass fibre, as a sorbent for oil-spills, *Mar. Pollut. Bull.* 49 (2004) 916–921.
- [9] A. Bayat, S.F. Aghamiri, A. Moheb, Oil sorption by synthesized exfoliated graphite (EG), *Iran. J. Chem. Eng.* 5 (1) (2008) 51–64.
- [10] D. Mysore, Th. Viraraghavan, Y. Jin, Treatment of oily waters using vermiculite, *Water Res.* 39 (2005) 2643–2653.
- [11] M.O. Adebajo, R.L. Frost, J.T. Klopogge, O. Carmody, S. Kokot, Porous materials for oil spill cleanup: a review of synthesis and absorbing properties, *J. Porous Mater.* 10 (2003) 159–170.
- [12] Q.F. Wei, R.R. Mather, A.F. Fotheringham, R.D. Yang, Evaluation of nonwoven polypropylene oil sorbents in marine oil-spill recovery, *Mar. Pollut. Bull.* 46 (2003) 780–783.
- [13] K. Sathasivam, M. Mas Haris, Adsorption kinetics and capacity of fatty acid-modified banana trunk fibers for oil in water, *Water Air Soil Pollut.* 213 (2010) 413–423.
- [14] T. Lim, X. Huang, Evaluation of kapok (*Ceiba pentandra* (L.) Gaertn.) as a natural hollow hydrophobic–oleophilic fibrous sorbent for oil spill cleanup, *Chemosphere* 66 (2007) 955–963.
- [15] A. Srinivasan, T. Viraraghavan, Removal of oil by walnut shell media, *Bioresour. Technol.* 99 (2008) 8217–8220.
- [16] M. Hussein, A.A. Amer, I.I. Sawsan, Oil spill sorption using carbonized pith bagasse: trial for practical Application, *Int. J. Environ. Sci. Tech.* 5 (2) (2008) 233–242.
- [17] X. Sun, R. Sun, J. Sun, Acetylation of rice straw with or without catalysts and its characterization as a natural sorbent in oil spill cleanup, *J. Agric. Food Chem.* 50 (2002) 6428–6433.
- [18] N.E. Thompson, G.C. Emmanuel, K.J. Adagadzu, N.B. Yusuf, Sorption studies of crude oil on acetylated rice husks, *Scholars Research Library, Arch. Appl. Sci. Res.* 2 (5) (2010) 142–151 [www.scholarsresearchlibrary.com](http://www.scholarsresearchlibrary.com).
- [19] M. Akhtar, M.I. Bhanger, Sh. Iqbal, S.M. Hasany, Sorption potential of rice husk for the removal of 2,4-dichlorophenol from aqueous solutions: kinetic and thermodynamic investigations, *J. Hazard. Mater. B* 128 (2006) 44–52.
- [20] S. Kumagai, K. Sasaki, Y. Shimizu, K. Takeda, Formaldehyde and acetaldehyde adsorption properties of heat-treated rice husks, *Sep. Purif. Technol.* 61 (2008) 398–403.
- [21] S.H. Yoon, M. Kim, B. Gil, Deacidification effects of rice hull-based adsorbents as affected by thermal and acid treatment, *LWT - Food Sci. Technol.* 44 (2011) 1572–1576.
- [22] M. Kim, S.H. Yoon, E. Choi, B. Gil, Comparison of the adsorbent performance between rice hull ash and rice hull silica gel according to their structural differences, *LWT - Food Sci. Technol.* 41 (2008) 701–706.
- [23] A.H. Mahvi, A. Maleki, A. Eslami, Potential of rice husk and rice husk ash for phenol removal in aqueous systems, *Am. J. Appl. Sci.* 1 (4) (2004) 321–326.
- [24] D.H. Lataye, I.M. Mishra, I.D. Mall, Pyridine sorption from aqueous solution by rice husk ash (RHA) and granular activated carbon (GAC): parametric, kinetic, equilibrium and thermodynamic aspects, *J. Hazard. Mater.* 154 (2008) 858–870.
- [25] S.A. Abo-El-Eneina, M.A. Eissab, A.A. Diafullahc, M.A. Rizkc, F.M. Mohamed, Removal of some heavy metals ions from wastewater by copolymer of iron and aluminum impregnated with active silica derived from rice husk ash, *J. Hazard. Mater.* 172 (2009) 574–579.
- [26] A.M. Yusofa, L.K. Keata, Z. Ibrahim, Z.A. Majida, N.A. Nizam, Kinetic and equilibrium studies of the removal of ammonium ions from aqueous solution by rice husk ash-synthesized zeolite Y and powdered and granulated forms of mordenite, *J. Hazard. Mater.* 174 (2010) 380–385.
- [27] S. Chandrasekhar, P.N. Pramada, Rice husk ash as an adsorbent for methylene blue-effect of ashing temperature, *Adsorption* 12 (2006) 27–43.
- [28] A. Imyim, E. Prapalimrunsi, Humic acids removal from water by aminopropyl functionalized rice husk ash, *J. Hazard. Mater.* 184 (2010) 775–781.
- [29] Z.A. Mansurov, M.M. Burkhitbaev, M.A. Biisenbaev, A.A. Kurmanbekov, Z.R. Ismagilov, N.V. Shikina, I.P. Andrievskaya, N.A. Rudina, Preparation of carbonized rice husk monoliths and modification of the porous structure by SiO<sub>2</sub> leaching, *Catal. Today* 147S (2009) S58–S65.
- [30] T. Watari, H. Tsubira, T. Torikai, M. Yada, S. Furuta, Preparation of porous carbon/silica composites from rice husk powder, *J. Ceram. Process. Res.* 4 (4) (2003) 177–180.
- [31] K.K. Kudaybergenov, E.K. Ongarbayev, Z.A. Mansurov, Carbonaceous composites from agricultural wastes for adsorption of hydrocarbon contamination in water, *Eurasian Chem. Technol. J.* 12 (2010) 151–156.
- [32] K.K. Kudaybergenov, E.K. Ongarbayev, Z.A. Mansurov, M.K. Musakulova, Carbonized sorbents on the base of rice husk for cleaning of water from oil contamination, In: Materials of VIII International scientific of Nadirov's reading, 8, 2010, pp. 531–536.
- [33] D. Kalderis, S. Bethanis, P. Paraskeva, E. Diamadopoulos, Production of activated carbon from bagasse and rice husk by a single-stage chemical activation method at low retention time, *Bioresour. Technol.* 99 (2008) 6809–6816.
- [34] S. Chandrasekhar, P.N. Pramada, J. Majeed, Effect of calcination temperature and heating rate on the optical properties and reactivity of rice husk ash, *J. Mater. Sci.* 41 (2006) 7926–7933.
- [35] X. Chen, L. Shuang-Shuang, Zh. Ping-Ping, L. Zhang, Y. Ye, Thermal destruction of rice hull in air and nitrogen, *J. Therm. Anal. Calorim.* 104 (2011) 1055–1062.
- [36] S.D. Genieva, S.Ch. Turmanova, A.S. Dimitrova, L.T. Vlaev, Characterization of rice husks and the products of the thermal degradation in air or nitrogen atmosphere, *J. Therm. Anal. Calorim.* 93 (2) (2008) 387–396.
- [37] A. Bharadwaj, Y. Wang, S. Sridhar, V.S. Arunachalam, Pyrolysis of rice husk, *Curr. Sci.* 87 (7) (2004) 981–986.